

® = registered Trademark of Ciba Holding Inc.

Tinuvin[®] 571

Liquid Benzotriazole UV Absorber

Characterization

Tinuvin 571 is a liquid ultraviolet light absorber (UVA) of the hydroxyphenyl benzotriazole class which imparts good light stability to a variety of polymers.


Chemical name

Phenol, 2-(2H-benzotriazol-2-yl)-4-methyl-6-dodecyl-, branched and linear

CAS number

125304-04-3

Chemical formula

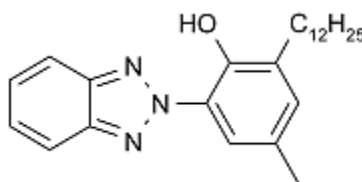

Molecular weight

394 g/mol

Applications

Tinuvin 571 can be applied in thermoplastic PUR, coating and integral foams, rigid and plasticized PVC, PVB, PMMA, PVDC, EVOH, EVA, hot cured unsaturated polyesters and spin finishes for PA, PET, PUR, and PP fibers. The product is also suitable for latices, waxes, adhesives, styrene homo- and copolymers, elastomers and polyolefins.

Features/benefits

Tinuvin 571 is highly soluble in many solvents, monomers, or intermediates and easily emulsifiable in water-based adhesives. It can be considered for use during polymerization as well as for topical applications on PVC sheets.

Tinuvin 571 features high compatibility in various substrates, low volatility even at elevated temperatures, and high absorption and protection efficiency.

Product forms

Clear viscous yellow liquid

Guidelines for use

Use levels of Tinuvin 571 range between 0.2 % and 5.0 %, depending on substrate and performance requirements of the final application.

In polyurethanes, the concentration levels for Tinuvin 571 range between 0.2 % and 0.5 % depending on substrate, processing conditions and long-term light stability requirements.

Concentration levels of Tinuvin 571 in PVC applications range from 0.3 % to 0.5 %. Concentrations up to 5 % can be used in co-extruded PVC.

In adhesives, the concentration levels for Tinuvin 571 range between 0.5% and 1.0%. Tinuvin 571 can be used alone or in a combination with other functional additives such as antioxidants (hindered phenols, phosphites) and HALS light stabilizers. Performance data are available in a variety of substrates.

Physical Properties


Melting Point	-56 °C
Flashpoint	> 200 °C
Specific Gravity (20 °C)	1.0 g/ml
Vapor Pressure (20 °C)	1.2 E-5 Pa

Solubility (20 °C)	g/100 g solution
Acetone	> 50
Chloroform	> 50
Ethanol	12
Ethyl acetate	> 50
n-Hexane	> 50
Methanol	1
Methylene chloride	> 50
Water	< 0.01

Volatility (pure substance; TGA, heating rate 20 °C/min in air)

Weight Loss %	Temperature °C
1.0	214
2.0	231
5.0	253

Absorbance spectrum (10 mg/l, Chloroform)

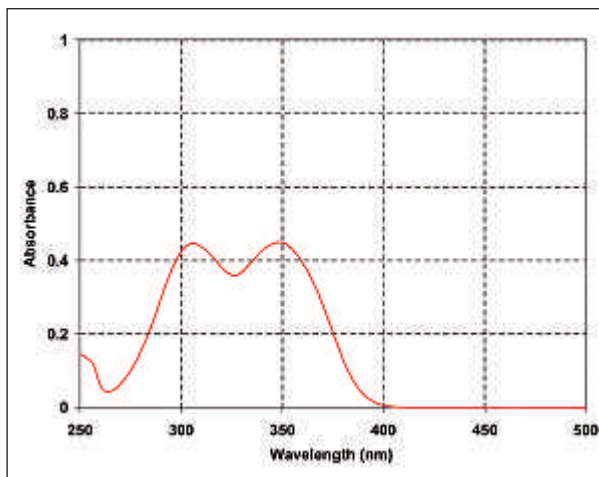

Tinuvin 571 exhibits strong absorbance in the 300–400 nm region and minimal absorbance in the visible region (> 400 nm) of the spectrum. The absorption maxima are at 303 nm and 343 nm ($\epsilon = 14'210 \text{ l/mol}\cdot\text{cm}$) in chloroform solution.

Handling & Safety

Tinuvin 571 exhibits a very low order of oral toxicity and does not present any abnormal problems in its handling or general use.

Detailed information on handling and any precautions to be observed in the use of the product(s) described in this leaflet can be found in our relevant health and safety information sheet.

Note

The descriptions, designs, data and information contained herein are presented in good faith, and are based on BASF's current knowledge and experience. They are provided for guidance only, and do not constitute the agreed contractual quality of the product or a part of BASF's terms and conditions of sale. Because many factors may affect processing or application/use of the product, BASF recommends that the reader carry out its own investigations and tests to determine the suitability of a product for its particular purpose prior to use. It is the responsibility of the recipient of product to ensure that any proprietary rights and existing laws and legislation are observed. No warranties of any kind, either expressed or implied, including, but not limited to, warranties of merchantability or fitness for a particular purpose, are made regarding products described or designs, data or information set forth herein, or that the products, descriptions, designs, data or information may be used without infringing the intellectual property rights of others. Any descriptions, designs, data and information given in this publication may change without prior information. The descriptions, designs, data and information furnished by BASF hereunder are given gratis and BASF assumes no obligation or liability for the descriptions, designs, data or information given or results obtained, all such being given and accepted at the reader's risk.

August 2010